


PRODUCT INFORMATION BASIC PROGRAM

AKROMID[®] A (PA 6.6)

AKROMID[®] B (PA 6)

AKROMID[®] C (PA 6.6/PA 6 Blend)

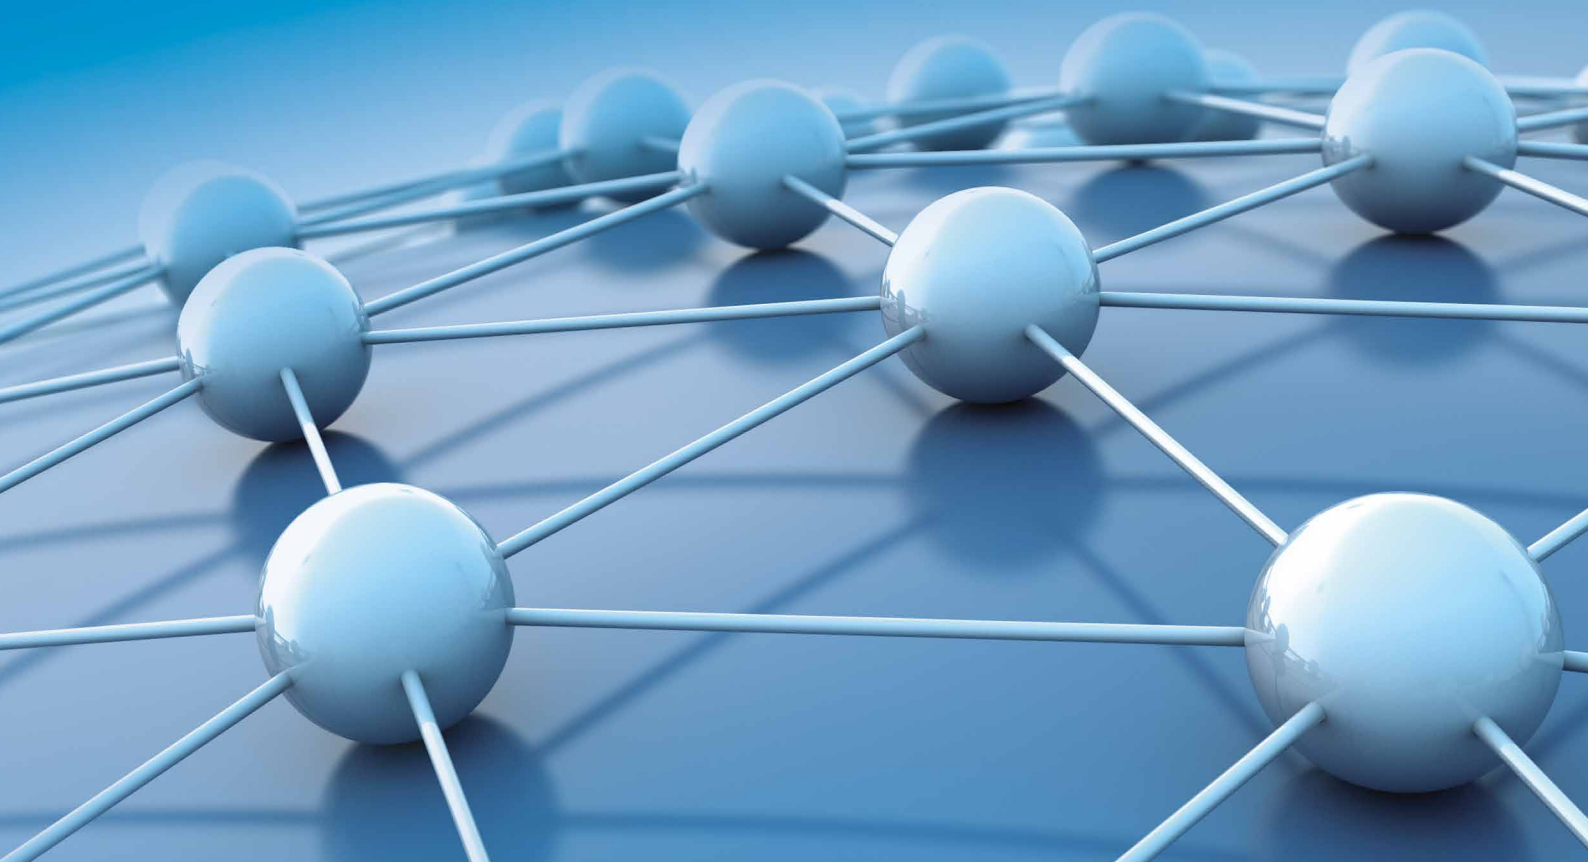

AKRO-PLASTIC 
Think Polyamide

AKRO-PLASTIC GmbH
Member of the Feddersen Group

Dear AKRO-PLASTIC customers,

with our brochure AKROMID® Basic Program we would like to give you a compact overview of our range of products AKROMID® A, B and C and associated application information. Since this information represents only partial aspects of our production possibilities and special demands are often made on compounds, you should always consult our application engineering department for questions or individual needs. Our engineers are able to offer competent advice on specific subjects, questions and problem solutions.

At AKRO-PLASTIC GmbH, we see ourselves not only as a producer, but also as a service provider. We constantly refine existing successful products, continually adapting them to the growing demands of the market. We set new standards with our certified quality management and our inhouse accredited test lab. In this endeavour, you the customer are an important interface. It is your needs, questions and demands that drive our efforts to continue this successful development.

And this joint effort should continue into the future.

AKROMID® A3 (PA 6.6)

| Typical values for natural color material at 23 °C | Test specification | Test method | Unit | A3 ¹ (2414) | | A3 GF 15 (2418) | | A3 GF 25 (2420) | | A28 GF 30 9 (4915) | | A3 GF 35 (2421) | | A3 GF 40 (1258) | | A28 GF 50 9 (5030) | | A3 GF 60 (2424) | | A 28 GF 30 1 GIT (4619) | | A3 GM 20/10 4 WIT (4529) | |
|--|-------------------------|---------------|-------------------|------------------------|---------|-----------------|---------|-----------------|---------|--------------------|---------|-----------------|---------|-----------------|---------|--------------------|---------|-----------------|---------|-------------------------|---------|--------------------------|---------|
| | | | | d.a.m. | cond. | d.a.m. | cond. | d.a.m. | cond. | d.a.m. | cond. | d.a.m. | cond. | d.a.m. | cond. | d.a.m. | cond. | d.a.m. | cond. | d.a.m. | cond. | d.a.m. | cond. |
| Mechanical properties | | | | | | | | | | | | | | | | | | | | | | | |
| Tensile modulus | 1 mm/min | ISO 527-1/2 | MPa | 3,200 | 1,100 | 6,400 | 3,700 | 8,500 | 6,000 | 9,600 | 7,000 | 11,600 | 8,400 | 13,100 | 9,800 | 16,000 | 12,000 | 20,500 | 15,800 | 9,200 | | 8,200 | 5,200 |
| Yield stress ¹ /Tensile stress at break | 5 mm/min | ISO 527-1/2 | MPa | 85/ | 50/ | /140 | /80 | /185 | /115 | /200 | /130 | /215 | /145 | /225 | /160 | /250 | /180 | /260 | /190 | 190 | | 175 | 100 |
| Elongation at break | 5 mm/min | ISO 527-1/2 | % | >20 | >50 | 3.5 | 12 | 3.6 | 6.5 | 3 | >6 | 3 | 5 | 3 | 4 | 2.5 | 3.5 | 2 | 2.5 | 3.5 | | 3.7 | 11.5 |
| Flexural modulus | 2 mm/min | ISO 178 | MPa | 2,800 | | 6,100 | | 7,600 | 6,200 | 8,800 | 7,200 | 10,000 | 8,000 | 12,000 | | 15,200 | 13,600 | 19,800 | | 8,700 | | 7,600 | 5,200 |
| Flexural stress | 2 mm/min | ISO 178 | MPa | 110 | | 200 | | 260 | 200 | 285 | 220 | 300 | 245 | 360 | | 380 | 310 | 400 | | 300 | | 260 | 170 |
| Charpy impact strength | 23 °C | ISO 179-1/1eU | kJ/m ² | n.b. | n.b. | 45 | 88 | 70 | 90 | 70 | 80 | 92 | 102 | 100 | 105 | 100 | 105 | 102 | 105 | 90 | | 65 | 80 |
| Charpy impact strength | -30 °C | ISO 179-1/1eU | kJ/m ² | n.b. | | 43 | | 64 | | 70 | | 90 | | 95 | | 80 | | 97 | | 70 | | 50 | 48 |
| Charpy notched impact strength | 23 °C | ISO 179-1/1eA | kJ/m ² | 5 | 13 | 7 | 10 | 10 | 13 | 12 | 16 | 15 | 19 | 17 | 20 | 19 | 23 | 19 | 22 | 15 | | 9 | 9.5 |
| Charpy notched impact strength | -30 °C | ISO 179-1/1eA | kJ/m ² | 2 | | 6 | | 9 | | 11 | | 13 | | 15 | | 16 | | 19 | | 13 | | 7 | 6.5 |
| Ball indentation hardness | HB 961/30 | ISO 2039-1 | MPa | | | 200 | | 225 | | 240 | | 255 | | 270 | | 290 | | 330 | | | | | |
| Electrical properties | | | | | | | | | | | | | | | | | | | | | | | |
| Volume resistivity | | IEC 60093 | Ohm x m | 1.0E+13 | 1.0E+10 | 1.0E+13 | 1.0E+10 | 1.0E+13 | 1.0E+10 | 1.0E+13 | 1.0E+10 | 1.0E+13 | 1.0E+10 | 1.0E+13 | 1.0E+10 | 1.0E+13 | 1.0E+10 | 1.0E+13 | 1.0E+10 | 1.0E+13 | 1.0E+10 | 1.0E+13 | 1.0E+10 |
| Surface resistivity | | IEC 60093 | Ohm | 1.0E+13 | 1.0E+10 | 1.0E+12 | 1.0E+10 | 1.0E+12 | 1.0E+10 | 1.0E+12 | 1.0E+10 | 1.0E+12 | 1.0E+10 | 1.0E+12 | 1.0E+10 | 1.0E+12 | 1.0E+10 | 1.0E+12 | 1.0E+10 | 1.0E+12 | 1.0E+10 | 1.0E+12 | 1.0E+10 |
| Comparative tracking index, CTI | Test solution A | IEC 60112 | | 600 | | 600 | | 600 | | 600 | | 600 | | 600 | | 600 | | 600 | | | | | |
| Thermal properties | | | | | | | | | | | | | | | | | | | | | | | |
| Melting point | DSC, 10 K/min | ISO 11357-1/3 | °C | 262 | | 262 | | 262 | | 262 | | 262 | | 262 | | 262 | | 262 | | 255 | | 262 | |
| Heat distortion temperature, HDT/A | 1.8 MPa | ISO 75-2 | °C | 75 | | 245 | | 255 | | 255 | | 255 | | 260 | | 260 | | 260 | | 260 | | 260 | |
| Heat distortion temperature, HDT/B | 0.45 MPa | ISO 75-2 | °C | 215 | | 260 | | 260 | | 260 | | 260 | | 260 | | 260 | | 260 | | 260 | | 260 | |
| Heat distortion temperature, HDT/C | 8 MPa | ISO 75-2 | °C | | | | | | | 210 | | 220 | | 225 | | 235 | | 235 | | 180 | | | |
| CLTE, flow | 23°C - 80°C | ISO 11359-1/2 | 1.0E-4/K | 0.71 | | 0.34 | | | | 0.19 | | | | | | 0.17 | | | | | | | |
| CLTE, transverse | 23°C - 80°C | ISO 11359-1/2 | 1.0E-4/K | 1.1 | | 1.11 | | | | 0.95 | | | | | | 0.88 | | | | | | | |
| Temperature index for 50 % loss of tensile strength ² | 5,000 h | IEC 216 | °C | 115 – 145 | | 160 – 175 | | 160 – 175 | | 160 – 175 | | 160 – 175 | | 160 – 175 | | 160 – 175 | | 160 – 175 | | 160 – 175 | | | |
| Temperature index for 50 % loss of tensile strength ² | 20,000 h | IEC 216 | °C | 100 – 120 | | 130 – 150 | | 130 – 150 | | 130 – 150 | | 130 – 150 | | 130 – 150 | | 130 – 150 | | 130 – 150 | | 130 – 150 | | | |
| Flammability | | | | | | | | | | | | | | | | | | | | | | | |
| Flammability acc. UL 94 | 1.6 mm | UL 94 | Class | V-2 | | HB | | HB | | HB | | HB | | HB | | HB | | HB | | HB | | HB | |
| Rate acc. FMVSS 302 (<100 mm/min) | >1 mm thickness | FMVSS 302 | mm/min | + | | + | | + | | + | | + | | + | | + | | + | | + | | + | |
| GWFI | 1.6 mm | IEC 60695-12 | °C | 750 | | 650 | | 650 | | 650 | | 650 | | 650 | | 650 | | 650 | | 650 | | 650 | |
| General properties | | | | | | | | | | | | | | | | | | | | | | | |
| Density | 23 °C | ISO 1183 | g/cm ³ | 1.14 | | 1.24 | | 1.32 | | 1.36 | | 1.40 | | 1.46 | | 1.57 | | 1.71 | | 1.36 | | 1.36 | |
| Content minerals/reinforcement | | ISO 1172 | % | - | | 15 | | 25 | | 30 | | 35 | | 40 | | 50 | | 60 | | 30 | | 30 | |
| Moisture absorption | 70 °C/62 % r. h. | ISO 1110 | % | 2.9 – 3.1 | | 2.5 – 2.7 | | 2 – 2.2 | | 1.9 – 2.1 | | 1.8 – 2 | | 1.7 – 1.9 | | 1.3 – 1.5 | | 1 – 1.2 | | | | 2 | |
| Water absorption | 23 °C/satur. | ISO 62 | % | 8 – 9 | | 6.7 – 7.3 | | 5.7 – 6.3 | | 5.2 – 5.8 | | 4.7 – 5.3 | | 4.3 – 4.7 | | 3.7 – 4.3 | | 3.2 – 3.7 | | | | | |
| Processing | | | | | | | | | | | | | | | | | | | | | | | |
| Flowability | Flowspiral ³ | AKRO | mm | 1,040 | | 990 | | 890 | | 950 | | 770 | | 720 | | 700 | | 530 | | 1,100 | | | |
| Processing shrinkage, flow | | ISO 294-4 | % | 1.9 | | 0.4 | | 0.2 | | 0.2 | | 0.2 | | 0.2 | | 0.3 | | 0.4 | | | | 0.4 | |
| Processing shrinkage, transverse | | ISO 294-4 | % | 2.3 | | 1.4 | | 1.3 | | 1.3 | | 1.3 | | 1.2 | | 1.2 | | 0.8 | | | | 0.8 | |

Despite identical nomenclature the AKROMID® materials produced by AKRO in China are identified by differential batch numbering.

"cond." test values = conditioned, measured on test specimens stored according to DIN EN ISO 1110
 "d.a.m." = dry as moulded test values = residual moisture content <0.10 %
 n.b. = not broken + = passed

¹ = yield stress and elongation at break: test speed 50 mm/min for non-reinforced compounds
² = depending on selected stabilisation, see application examples
³ = mould temperature: 100 °C, melt temperature: 320 °C, injection pressure: 750 bar, cross section of flow spiral: 7 mm x 3.5 mm

AKROMID® B3 (PA 6)

| Typical values for natural color material at 23 °C | | | Test specification | Test method | Unit | B3 ¹ (2500) | B3 GF 15 (2469) | B3 GF 20 (2470) | B3 GF 25 (2471) | B3 GF 30 (2472) | B3 GF 35 (2473) | B3 GF 40 (2474) | B3 GF 50 (2475) | B28 GF 60 9 (4662) | B3 GF 30 2 GIT (4618) | | | | | | | | |
|--|-------------------------|---------------|--------------------|-------------|---------|---------------------------|--------------------|--------------------|--------------------|--------------------|--------------------|--------------------|--------------------|-----------------------|--------------------------|-----------|---------|-----------|---------|-----------|---------|-----------|---------|
| | | | | | | d.a.m. | cond. | d.a.m. | cond. | d.a.m. | cond. | d.a.m. | cond. | d.a.m. | cond. | d.a.m. | cond. | d.a.m. | cond. | d.a.m. | cond. | | |
| Mechanical properties | | | | | | | | | | | | | | | | | | | | | | | |
| Tensile modulus | 1 mm/min | ISO 527-1/2 | MPa | 3,600 | 1,200 | 6,100 | 3,300 | 6,800 | 4,200 | 8,500 | 5,100 | 10,300 | 6,200 | 11,500 | 7,300 | 12,800 | 8,200 | 17,000 | 11,000 | 21,000 | 13,500 | 9,100 | 5,500 |
| Yield stress ¹ /Tensile stress at break | 5 mm/min | ISO 527-1/2 | MPa | 85/ | 45/ | /120 | /75 | /150 | /85 | /160 | /100 | /185 | /110 | /195 | /120 | /205 | /130 | /230 | /145 | 250 | 150 | 175 | 110 |
| Elongation at break | 5 mm/min | ISO 527-1/2 | % | >20 | >50 | 3 | 10 | 3.5 | 7.5 | 3.5 | 6.5 | 3 | 6.1 | 3 | 5 | 3 | 5 | 2.5 | 4.5 | 2.5 | 3.5 | 3 | 5 |
| Flexural modulus | 2 mm/min | ISO 178 | MPa | 3,100 | | 5,200 | | 6,100 | | 7,000 | | 8,500 | | 10,000 | | 10,300 | | 14,900 | | 19,000 | | | |
| Flexural stress | 2 mm/min | ISO 178 | MPa | 120 | | 180 | | 230 | | 245 | | 270 | | 285 | | 300 | | 340 | | 370 | | | |
| Charpy impact strength | 23 °C | ISO 179-1/1eU | kJ/m ² | n.b. | n.b. | 52 | 95 | 73 | 88 | 85 | 90 | 95 | 105 | 100 | 110 | 100 | 110 | 100 | 110 | 90 | 95 | 75 | 80 |
| Charpy impact strength | -30 °C | ISO 179-1/1eU | kJ/m ² | n.b. | | 43 | | 65 | | 80 | | 85 | | 90 | | 90 | | 90 | | 88 | | | |
| Charpy notched impact strength | 23 °C | ISO 179-1/1eA | kJ/m ² | 5 | 16 | 7 | 11 | 9 | 14 | 12 | 16 | 13 | 18 | 15 | 21 | 17 | 23 | 20 | 26 | 20 | 25 | 12 | 17 |
| Charpy notched impact strength | -30 °C | ISO 179-1/1eA | kJ/m ² | 2 | | 6 | | 8 | | 10 | | 12 | | 13 | | 14 | | 16 | | 19 | | | |
| Ball indentation hardness | HB 961/30 | ISO 2039-1 | MPa | | | 180 | | 200 | | 215 | | 230 | | 240 | | 250 | | 270 | | 290 | | | |
| Electrical properties | | | | | | | | | | | | | | | | | | | | | | | |
| Volume resistivity | | IEC 60093 | Ohm x m | 1.0E+13 | 1.0E+10 | 1.0E+13 | 1.0E+10 | 1.0E+13 | 1.0E+10 | 1.0E+13 | 1.0E+10 | 1.0E+13 | 1.0E+10 | 1.0E+13 | 1.0E+10 | 1.0E+13 | 1.0E+10 | 1.0E+13 | 1.0E+10 | 1.0E+13 | 1.0E+10 | 1.0E+13 | 1.0E+10 |
| Surface resistivity | | IEC 60093 | Ohm | 1.0E+12 | 1.0E+10 | 1.0E+12 | 1.0E+10 | 1.0E+12 | 1.0E+10 | 1.0E+12 | 1.0E+10 | 1.0E+12 | 1.0E+10 | 1.0E+12 | 1.0E+10 | 1.0E+12 | 1.0E+10 | 1.0E+12 | 1.0E+10 | 1.0E+12 | 1.0E+10 | 1.0E+12 | 1.0E+10 |
| Comparative tracking index, CTI | Test solution A | IEC 60112 | | 600 | | 600 | | 600 | | 600 | | 600 | | 600 | | 600 | | 600 | | 600 | | 600 | |
| Thermal properties | | | | | | | | | | | | | | | | | | | | | | | |
| Melting point | DSC, 10 K/min | ISO 11357-1/3 | °C | 220 | | 220 | | 220 | | 220 | | 220 | | 220 | | 220 | | 220 | | 220 | | 220 | |
| Heat distortion temperature, HDT/A | 1.8 MPa | ISO 75-2 | °C | 60 | | 205 | | 210 | | 210 | | 210 | | 215 | | 215 | | 220 | | 220 | | 220 | |
| Heat distortion temperature, HDT/B | 0.45 MPa | ISO 75-2 | °C | 180 | | 220 | | 220 | | 220 | | 220 | | 220 | | 220 | | 220 | | 220 | | 220 | |
| Heat distortion temperature, HDT/C | 8 MPa | ISO 75-2 | °C | | | | | | | | | 150 | | 165 | | 170 | | 185 | | 190 | | | |
| CLTE, flow | 23°C - 80°C | ISO 11359-1/2 | 1.0E-4/K | | | | | | | | | 0,16 | | | | | 0,11 | | | | | | |
| CLTE, transverse | 23°C - 80°C | ISO 11359-1/2 | 1.0E-4/K | | | | | | | | | 0,95 | | | | | 0,94 | | | | | | |
| Temperature index for 50 % loss of tensile strength ² | 5,000 h | IEC 216 | °C | 100 – 140 | | 160 – 175 | | 160 – 175 | | 160 – 175 | | 160 – 175 | | 160 – 175 | | 160 – 175 | | 160 – 175 | | 160 – 175 | | 160 – 175 | |
| Temperature index for 50 % loss of tensile strength ² | 20,000 h | IEC 216 | °C | 90 – 120 | | 130 – 150 | | 130 – 150 | | 130 – 150 | | 130 – 150 | | 130 – 150 | | 130 – 150 | | 130 – 150 | | 130 – 150 | | 130 – 150 | |
| Flammability | | | | | | | | | | | | | | | | | | | | | | | |
| Flammability acc. UL 94 | 1.6 mm | UL 94 | Class | V – 2 | | HB | | HB | | HB | | HB | | HB | | HB | | HB | | HB | | HB | |
| Rate acc. FMVSS 302 (<100 mm/min) | >1 mm thickness | FMVSS 302 | mm/min | + | | + | | + | | + | | + | | + | | + | | + | | + | | + | |
| GWFI | 1.6 mm | IEC 60695-12 | °C | 750 | | 650 | | 650 | | 650 | | 650 | | 650 | | 650 | | 650 | | 650 | | 650 | |
| General properties | | | | | | | | | | | | | | | | | | | | | | | |
| Density | 23 °C | ISO 1183 | g/cm ³ | 1.13 | | 1.23 | | 1.27 | | 1.31 | | 1.36 | | 1.41 | | 1.46 | | 1.56 | | 1.70 | | 1.36 | |
| Content minerals/reinforcement | | ISO 1172 | % | – | | 15 | | 20 | | 25 | | 30 | | 35 | | 40 | | 50 | | 60 | | 30 | |
| Moisture absorption | 70 °C/62 % r. h. | ISO 1110 | % | 2.6 – 3.4 | | 2.6 – 2.9 | | 2.4 – 2.7 | | 2.2 – 2.5 | | 2.1 – 2.3 | | 1.8 – 2.1 | | 1.5 – 1.8 | | 1.3 – 1.6 | | 0.9 – 1.2 | | 2.2 | |
| Water absorption | 23 °C/satur. | ISO 62 | % | 9 – 10 | | 7.7 – 8.3 | | 7.4 – 7.7 | | 6.8 – 7.4 | | 6.3 – 6.9 | | 5.9 – 6.5 | | 5.2 – 5.7 | | 4.5 – 5.1 | | 3.9 – 4.4 | | | |
| Processing | | | | | | | | | | | | | | | | | | | | | | | |
| Flowability | Flowspiral ³ | AKRO | mm | 1,070 | | 870 | | 800 | | 720 | | 660 | | 610 | | 540 | | 430 | | 470 | | | |
| Processing shrinkage, flow | | ISO 294-4 | % | 1.1 | | 0.3 | | 0.2 | | 0.2 | | 0.1 | | 0.1 | | 0.1 | | 0.2 | | 0.3 | | | |
| Processing shrinkage, transverse | | ISO 294-4 | % | 1 | | 0.7 | | 0.8 | | 0.8 | | 0.8 | | 0.8 | | 0.9 | | 0.9 | | 0.7 | | | |

Despite identical nomenclature the AKROMID® materials produced by AKRO in China are identified by differential batch numbering.

"cond." test values = conditioned, measured on test specimens stored according to DIN EN ISO 1110
 "d.a.m." = dry as moulded test values = residual moisture content <0.10 %
 n.b. = not broken + = passed

¹ = yield stress and elongation at break: test speed 50 mm/min for non-reinforced compounds
² = depending on selected stabilisation, see application examples
³ = mould temperature: 80 °C, melt temperature: 270 °C, injection pressure: 750 bar, cross section of flow spiral: 7 mm x 3.5 mm

AKROMID® B3 (PA 6)

AKROMID® C3 (PA 6.6/6 Blend)

| Typical values for natural color material at 23 °C | Test specification | Test method | Unit | B3 black (20004) | | B3 GF 20 1 black (20001) | | B3 GF 30 1 black (20000) | | B3 GF 30 5 black (20009) | | B3 GF 50 1 black (20008) | |
|--|-------------------------|---------------|-------------------|------------------|---------|--------------------------|---------|--------------------------|---------|--------------------------|---------|--------------------------|---------|
| | | | | d.a.m. | cond. | d.a.m. | cond. | d.a.m. | cond. | d.a.m. | cond. | d.a.m. | cond. |
| Mechanical properties | | | | | | | | | | | | | |
| Tensile modulus | 1 mm/min | ISO 527-1/2 | MPa | 3,200 | 1,100 | 7,000 | 4,000 | 9,500 | 6,000 | 9,500 | 6,000 | 17,000 | 10,000 |
| Yield stress ¹ /Tensile stress at break | 5 mm/min | ISO 527-1/2 | MPa | 80 | 40 | 145 | 80 | 175 | 100 | 175 | 100 | 210 | 120 |
| Elongation at break | 5 mm/min | ISO 527-1/2 | % | >20 | >40 | 3 | 7 | 3 | 5 | 3 | 5 | 3 | 5 |
| Flexural modulus | 2 mm/min | ISO 178 | MPa | | | | | | | | | | |
| Flexural stress | 2 mm/min | ISO 178 | MPa | | | | | | | | | | |
| Charpy impact strength | 23 °C | ISO 179-1/1eU | kJ/m ² | n.b. | n.b. | 60 | 75 | 95 | 105 | 95 | 105 | 100 | 105 |
| Charpy impact strength | -30 °C | ISO 179-1/1eU | kJ/m ² | | | | | | | | | | |
| Charpy notched impact strength | 23 °C | ISO 179-1/1eA | kJ/m ² | | | 8 | 12 | 13 | 18 | 13 | 18 | 18 | 22 |
| Charpy notched impact strength | -30 °C | ISO 179-1/1eA | kJ/m ² | | | | | | | | | | |
| Ball indentation hardness | HB 961/30 | ISO 2039-1 | MPa | | | 200 | | 230 | | 230 | | 270 | |
| Electrical properties | | | | | | | | | | | | | |
| Volume resistivity | | IEC 60093 | Ohm x m | 1.0E+13 | 1.0E+10 | 1.0E+13 | 1.0E+10 | 1.0E+13 | 1.0E+10 | 1.0E+13 | 1.0E+10 | 1.0E+13 | 1.0E+10 |
| Surface resistivity | | IEC 60093 | Ohm | 1.0E+12 | 1.0E+10 | 1.0E+12 | 1.0E+10 | 1.0E+12 | 1.0E+10 | 1.0E+12 | 1.0E+10 | 1.0E+12 | 1.0E+10 |
| Comparative tracking index, CTI | Test solution A | IEC 60112 | | 600 | | 600 | | 600 | | 600 | | 600 | |
| Thermal properties | | | | | | | | | | | | | |
| Melting point | DSC, 10 K/min | ISO 11357-1/3 | °C | d.a.m. | | d.a.m. | | d.a.m. | | d.a.m. | | d.a.m. | |
| Heat distortion temperature, HDT/A | 1.8 MPa | ISO 75-2 | °C | 220 | | 220 | | 220 | | 220 | | 220 | |
| Heat distortion temperature, HDT/B | 0.45 MPa | ISO 75-2 | °C | 60 | | 210 | | 210 | | 210 | | 220 | |
| Heat distortion temperature, HDT/C | 8 MPa | ISO 75-2 | °C | 180 | | 220 | | 220 | | 220 | | 220 | |
| CLTE, flow | 23°C - 80°C | ISO 11359-1/2 | 1.0E-4/K | | | | | 0.16 | | 0.16 | | 0.11 | |
| CLTE, transverse | 23°C - 80°C | ISO 11359-1/2 | 1.0E-4/K | | | | | 0.95 | | 0.95 | | 0.94 | |
| Temperature index for 50 % loss of tensile strength ² | 5,000 h | IEC 216 | °C | | | | | | | | | 160 – 175 | |
| Temperature index for 50 % loss of tensile strength ² | 20,000 h | IEC 216 | °C | | | | | | | | | 130 – 150 | |
| Flammability | | | | | | | | | | | | | |
| Flammability acc. UL 94 | 1.6 mm | UL 94 | Class | V-2 | | HB | | HB | | HB | | HB | |
| Rate acc. FMVSS 302 (<100 mm/min) | >1 mm thickness | FMVSS 302 | mm/min | + | | + | | + | | + | | + | |
| GWFI | 1.6 mm | IEC 60695-12 | °C | 750 | | 650 | | 650 | | 650 | | 650 | |
| General properties | | | | | | | | | | | | | |
| Density | 23 °C | ISO 1183 | g/cm ³ | 1.13 | | 1.27 | | 1.36 | | 1.36 | | 1.56 | |
| Content minerals/reinforcement | | ISO 1172 | % | | | 20 | | 30 | | 30 | | 50 | |
| Moisture absorption | 70 °C/62 % r. h. | ISO 1110 | % | 2.6 – 3.4 | | 2.4 – 2.7 | | 2.1 – 2.3 | | 2.1 – 2.3 | | 1.3 – 1.6 | |
| Water absorption | 23 °C/satur. | ISO 62 | % | 9 – 10 | | 7.4 – 7.7 | | 6.3 – 6.9 | | 6.3 – 6.9 | | 4.5 – 5.1 | |
| Processing | | | | | | | | | | | | | |
| Flowability | Flowspiral ³ | AKRO | mm | | | 800 | | 660 | | 660 | | 430 | |
| Processing shrinkage, flow | | ISO 294-4 | % | | | 0.2 | | 0.1 | | 0.1 | | 0.2 | |
| Processing shrinkage, transverse | | ISO 294-4 | % | | | 0.8 | | 0.8 | | 0.8 | | 0.9 | |

Despite identical nomenclature the AKROMID® materials produced by AKRO in China are identified by differential batch numbering.

"cond." test values = conditioned, measured on test specimens stored according to DIN EN ISO 1110
 "d.a.m." = dry as moulded test values = residual moisture content <0.10 %
 n.b. = not broken + = passed

| C3 1' (4546) | | C3 GF 50 XTC (4946) | | C3 GF 50 1 (4401) | | C3 GF 60 1 (4659) | | C3 GF 30 5 XTC (4499) | |
|--------------|---------|---------------------|---------|-------------------|---------|-------------------|---------|-----------------------|---------|
| d.a.m. | cond. | d.a.m. | cond. | d.a.m. | cond. | d.a.m. | cond. | d.a.m. | cond. |
| 3,100 | 1,100 | 17,500 | | 16,000 | 11,000 | 21,300 | 13,200 | 9,900 | 6,000 |
| 80 | 45 | /260 | | 240 | 165 | 270 | 180 | 190 | /115 |
| 5 | >50 | 3.2 | | 2.5 | 4 | 2.3 | 4 | 3.7 | 6.5 |
| 3,000 | | 17,000 | | 16,200 | | 22,500 | | | 6,200 |
| 115 | | 415 | | 360 | | 425 | | | 200 |
| n.b. | n.b. | 125 | | 95 | 100 | 96 | 103 | 95 | 90 |
| | | 125 | | | | | | | |
| 3 | 13 | 25 | | 20 | 20 | 19 | 24 | 13 | 13 |
| | | 25 | | 20 | | | | | |
| | | | | | | | | | |
| 1.0E+13 | 1.0E+10 | 1.0E+13 | 1.0E+10 | 1.0E+13 | 1.0E+10 | 1.0E+13 | 1.0E+10 | 1.0E+13 | 1.0E+10 |
| 1.0E+13 | 1.0E+10 | 1.0E+12 | 1.0E+10 | 1.0E+12 | 1.0E+10 | 1.0E+12 | 1.0E+10 | 1.0E+12 | 1.0E+10 |
| 600 | | 600 | | 600 | | 600 | | 600 | |
| d.a.m. | | d.a.m. | | d.a.m. | | d.a.m. | | d.a.m. | |
| 260 | | 255 | | 260 | | 260 | | 255 | |
| | | 230 | | 250 | | | | 230 | |
| 185 | | 190 | | | | 255 | | 250 | |
| | | | | 220 | | 212 | | | |
| 100 – 140 | | | | 160 – 175 | | 160 – 175 | | | |
| 90 – 120 | | | | 130 – 150 | | 130 – 150 | | | |
| V-2 | | HB | | HB | | HB | | HB | |
| + | | + | | + | | + | | + | |
| | | | | | | | | | |
| 1.14 | | | | 1.57 | | 1.71 | | 1.39 | |
| - | | 50 | | 50 | | 60 | | 30 | |
| 2.6 | | | | 1.4 | | 1.1 | | | |
| 1,600 | | | | 650 | | 580 | | | |
| 1.2 | | | | 0.3 | | 0.4 | | | |
| 1.9 | | | | 1.2 | | 0.8 | | | |

¹ = yield stress and elongation at break: test speed 50 mm/min for non-reinforced compounds

² = depending on selected stabilisation, see application examples

³ = mould temperature: 90 °C, melt temperature: 300 °C, injection pressure: 750 bar, cross section of flow spiral: 7 mm x 3.5 mm

AKROMID® A/B (impact resistant)

AKROMID® A EN (electrical neutral)

| Typical values for natural color material at 23 °C | Test specification | Test method | Unit | A3 1 S3 ¹ (1139) | | A3 S1 ¹ (1071) | | B3 GF 30 S1 (2091) | | B3 GF 15 S1 (3228) | | B3 S1 (3726) | |
|--|------------------------|---------------|-------------------|-----------------------------|-------|---------------------------|-------|--------------------|-------|--------------------|-------|--------------|-------|
| | | | | d.a.m. | cond. | d.a.m. | cond. | d.a.m. | cond. | d.a.m. | cond. | d.a.m. | cond. |
| Mechanical properties | | | | | | | | | | | | | |
| Tensile modulus | 1 mm/min | ISO 527-1/2 | MPa | 2,700 | 1,300 | 2,000 | 900 | 7,500 | 4,200 | 6,000 | 3,100 | 2,000 | 550 |
| Yield stress ¹ /Tensile stress at break | 5 mm/min | ISO 527-1/2 | MPa | 63 | 45 | 50 | 40 | 125 | 70 | 120 | 75 | 50/ | 45/ |
| Elongation at break | 5 mm/min | ISO 527-1/2 | % | >35 | >100 | >50 | >100 | 6 | 13 | 4 | 10 | > 50 | > 100 |
| Flexural modulus | 2 mm/min | ISO 178 | MPa | 2,500 | | 1,950 | | 6,400 | | 5,300 | | 1,500 | |
| Flexural stress | 2 mm/min | ISO 178 | MPa | 90 | | | | 190 | | 175 | | 65 | |
| Charpy impact strength | 23 °C | ISO 179-1/1eU | kJ/m ² | n.b. | n.b. | n.b. | n.b. | 110 | 135 | 70 | 95 | n.b. | n.b. |
| Charpy impact strength | -30 °C | ISO 179-1/1eU | kJ/m ² | n.b. | n.b. | n.b. | n.b. | >100 | >100 | 50 | 45 | n.b. | n.b. |
| Charpy notched impact strength | 23 °C | ISO 179-1/1eA | kJ/m ² | 15 | 95 | >80 | >100 | 35 | 45 | 4 | 14 | 45 | 110 |
| Charpy notched impact strength | -30 °C | ISO 179-1/1eA | kJ/m ² | 10 | 13 | 35 | 35 | 25 | 22 | 6 | 5 | 55 | 40 |
| Ball indentation hardness | HB 961/30 | ISO 2039-1 | MPa | | | | | | | | | | |
| Electrical properties | | | | | | | | | | | | | |
| Volume resistivity | | IEC 60093 | Ohm x m | 1.0E+15 | | 1.0E+15 | | | | | | 1.0E+13 | |
| Surface resistivity | | IEC 60093 | Ohm | 1.0E+14 | | 1.0E+14 | | | | | | 1.0E+12 | |
| Comparative tracking index, CTI | Test solution A | IEC 60112 | | 600 | | 600 | | | | | | | |
| Thermal properties | | | | | | | | | | | | | |
| Melting point | DSC, 10 K/min | ISO 11357-1/3 | °C | 262 | | 262 | | 220 | | 220 | | 220 | |
| Heat distortion temperature, HDT/A | 1.8 MPa | ISO 75-2 | °C | 70 | | 70 | | 200 | | 200 | | 50 | |
| Heat distortion temperature, HDT/B | 0.45 MPa | ISO 75-2 | °C | 213 | | 152 | | | | | | | |
| Heat distortion temperature, HDT/C | 8 MPa | ISO 75-2 | °C | | | | | | | | | | |
| CLTE, flow | 23°C - 80°C | ISO 11359-1/2 | 1.0E-4/K | | | | | | | | | | |
| CLTE, transverse | 23°C - 80°C | ISO 11359-1/2 | 1.0E-4/K | | | | | | | | | | |
| Temperature index for 50 % loss of tensile strength ² | 5,000 h | IEC 216 | °C | | | | | | | | | 160 – 175 | |
| Temperature index for 50 % loss of tensile strength ² | 20,000 h | IEC 216 | °C | | | | | | | | | 130 – 150 | |
| Flammability | | | | | | | | | | | | | |
| Flammability acc. UL 94 | 1.6 mm | UL 94 | Class | HB | | HB | | HB | | HB | | HB | |
| Rate acc. FMVSS 302 (<100 mm/min) | >1 mm thickness | FMVSS 302 | mm/min | + | | + | | + | | + | | + | |
| GWFI | 1.6 mm | IEC 60695-12 | °C | | | | | | | | | | |
| General properties | | | | | | | | | | | | | |
| Density | 23 °C | ISO 1183 | g/cm ³ | 1.10 | | 1.07 | | 1.28 | | 1.22 | | 1.07 | |
| Content minerals/reinforcement | | ISO 1172 | % | | | | | 30 | | 15 | | | |
| Moisture absorption | 70 °C/62 % r. h. | ISO 1110 | % | 2.1 | | 2 | | 1.4 | | 2.3 | | | |
| Water absorption | 23 °C/satur. | ISO 62 | % | | | | | | | | | | |
| Processing | | | | | | | | | | | | | |
| Flowability | Flowsipal ³ | AKRO | mm | 800 | | 770 | | 530 | | 730 | | 600 | |
| Processing shrinkage, flow | | ISO 294-4 | % | 2.1 | | 1.4 | | 0.4 | | 0.6 | | 1.5 | |
| Processing shrinkage, transverse | | ISO 294-4 | % | 2.2 | | 1.4 | | 0.9 | | 0.9 | | 1.9 | |

Despite identical nomenclature the AKROMID® materials produced by AKRO in China are identified by differential batch numbering.

"cond." test values = conditioned, measured on test specimens stored according to DIN EN ISO 1110
 "d.a.m." = dry as moulded test values = residual moisture content <0.10 %
 n.b. = not broken + = passed

| A4 5 EN natural (3162) | | A3 GF 20 1 EN black (5935) | | A3 GF 30 1 EN black (5646) | | A3 GF 35 1 EN black (5300) | | A3 GF 50 1 EN black (5737) | |
|------------------------|---------|----------------------------|---------|----------------------------|---------|----------------------------|---------|----------------------------|---------|
| d.a.m. | cond. | d.a.m. | cond. | d.a.m. | cond. | d.a.m. | cond. | d.a.m. | cond. |
| 3,500 | 1,400 | 7,200 | 4,600 | 10,000 | 7,100 | 11,600 | 8,400 | 16,700 | 12,600 |
| /95 | /55 | /160 | /100 | /200 | /130 | /215 | /145 | /250 | /180 |
| 4.5 | 20 | 3.5 | 8 | 3 | >6 | 3 | 5 | 2.5 | 3.5 |
| 2,900 | 1,500 | 7,000 | 5,000 | 8,800 | 7,200 | 10,000 | 8,000 | 15,200 | 13,600 |
| 50 | 15 | 235 | 165 | 285 | 220 | 300 | 245 | 380 | 310 |
| n.b. | n.b. | 60 | 86 | 85 | 95 | 92 | 102 | 105 | 110 |
| n.b. | n.b. | 48 | | 80 | | 90 | | 105 | |
| 5 | 15 | 9 | | 12 | 16 | 15 | 19 | 19 | 23 |
| | | 8 | 11 | 11 | | 13 | | 16 | |
| | | | | 240 | | 255 | | 290 | |
| 1.0E+13 | 1.0E+10 | 1.0E+13 | 1.0E+10 | 1.0E+13 | 1.0E+10 | 1.0E+13 | 1.0E+10 | 1.0E+13 | 1.0E+10 |
| 1.0E+13 | 1.0E+10 | 1.0E+12 | 1.0E+10 | 1.0E+12 | 1.0E+10 | 1.0E+12 | 1.0E+10 | 1.0E+12 | 1.0E+10 |
| 600 | | 600 | | 600 | | 600 | | 601 | |
| d.a.m. | | d.a.m. | | d.a.m. | | d.a.m. | | d.a.m. | |
| 262 | | 262 | | 262 | | 262 | | 262 | |
| | | 250 | | 255 | | 255 | | 260 | |
| | | 260 | | 260 | | 260 | | 260 | |
| | | | | 210 | | 220 | | 235 | |
| | | | | 0.19 | | | | 0.17 | |
| | | | | 0.95 | | | | 0.88 | |
| | | 160 – 175 | | 160 – 175 | | 160 – 175 | | 160 – 175 | |
| | | 130 – 150 | | 130 – 150 | | 130 – 150 | | 130 – 150 | |
| | | HB | | HB | | HB | | HB | |
| | | + | | + | | + | | + | |
| | | 650 | | 650 | | 650 | | 650 | |
| 1.14 | | 1.28 | | 1.36 | | 1.40 | | 1.57 | |
| | | 20 | | 30 | | 35 | | 50 | |
| 2.4 – 2.8 | | 2.3 – 2.5 | | 1.9 – 2.1 | | 1.8 – 2 | | 1.3 – 1.5 | |
| | | 6.7 – 7.2 | | 5.2 – 5.8 | | 4.7 – 5.3 | | 3.7 – 4.3 | |
| | | 950 | | 830 | | 770 | | 600 | |
| | | 0.3 | | 0.2 | | 0.2 | | 0.3 | |
| | | 1.3 | | 1.3 | | 1.3 | | 1.2 | |

¹ = yield stress and elongation at break: test speed 50 mm/min for non-reinforced compounds

² = depending on selected stabilisation, see application examples

³ = mould temperature: 100 °C, melt temperature: 320 °C, injection pressure: 750 bar, cross section of flow spiral: 7 mm x 3.5 mm

Product characterisation


Stabilisation with shielding technology (Fig. 1)




Tensile bar made of C3 GF 30 5 XTC natural (4499) after 1,000 h at 210 °C

Rising to the challenge of meeting steadily increasing demands for cost-effective materials with greater heat resistance, AKRO-PLASTIC has developed AKROMID® C3 GF 30 5 XTC, a compound with an exceptional heat ageing resistance at temperatures of around 200 °C. Stabilisation in AKROMID® C3 GF 30 5 XTC is based on shielding technology (see Fig. 1) and is electrically neutral. Potential applications can be found primarily in the automotive industry, where alternatives to conventional thermoplastics are sought due to increasing temperatures in the engine compartment. Even after an ageing treatment lasting 5,000 h at 210 °C, hardly any decrease in tensile stress at break is observed (see Fig. 2). The strain following this conditioning is still significantly greater than 2 % (see Fig. 3). And AKROMID® C3 GF 30 5 XTC is just as easy to process as standard AKROMID® compounds. As with other polyamide compounds, the strengths are extremely dependent on the temperature (see Fig. 4).


Resistance based on exposure time (Fig. 2)

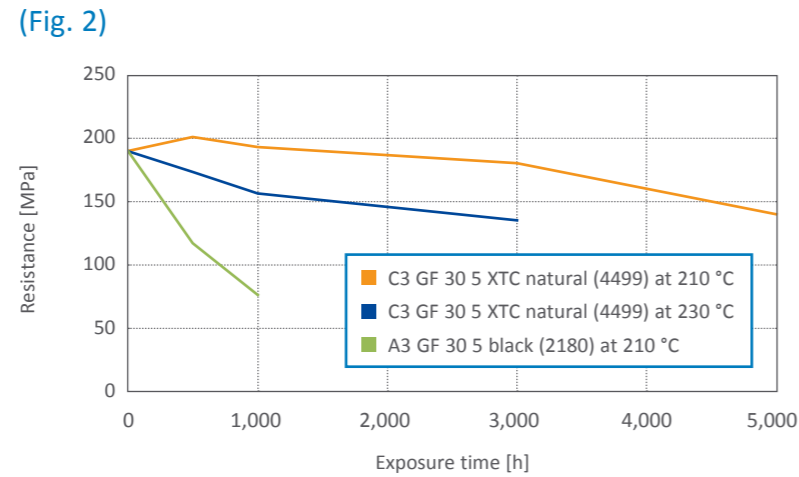

Elongation at break based on exposure time (Fig. 3)

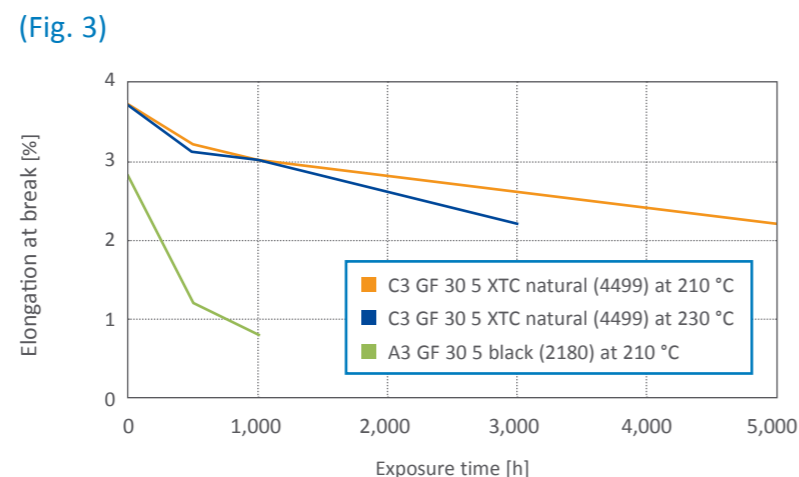

Stress-strain curves at temperature (Fig. 4)

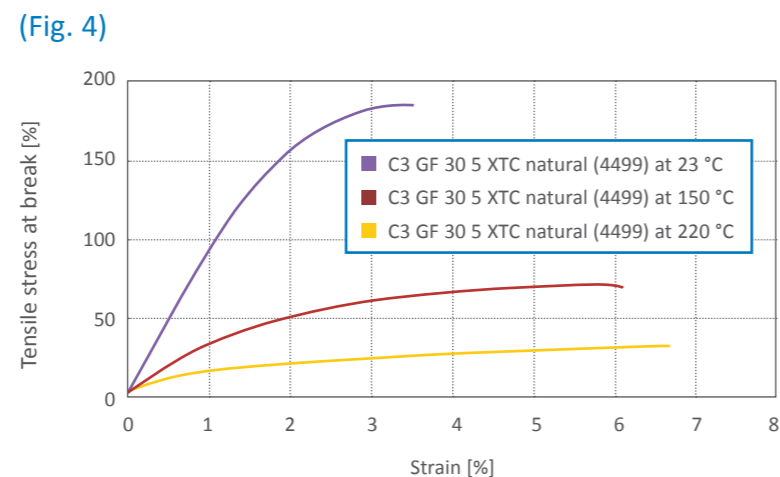

Electrically neutral compounds

Certificate of analysis (Fig. 5)

AKRO-PLASTIC GmbH
Member of the Feddersen Group

Certificate of analysis according to EN 10204-3.1

Description of product
Item number: 17913
Type: AKROMID® A3 GF 30 1 EN natural (5636)

Production data
Lot-no.: F502 17901

Customer data
Order-no.: see order

Testresults

| Testing* | Norm | Testing condition | Actual value | Unit |
|-------------------------|---------------------------|-------------------|--------------|------|
| Residual humidity | DIN EN ISO 15512 method B | | 0.07 | % |
| Bromine <1 ppm | 35.08.PV.041 | | ok | |
| Iodine <1 ppm | 35.08.PV.041 | | ok | |
| Tensile modulus | DIN EN ISO 527-2/1A | 1 mm/min | 9,890 | MPa |
| Tensile stress at break | DIN EN ISO 527-2/1A | 5 mm/min | 195 | MPa |
| Elongation at break | DIN EN ISO 527-2/1A | 5 mm/min | 3.2 | % |
| Ash content | DIN EN ISO 1172 method A | 625 °C | 29.9 | % |

Date of release: 20.04.2015, 12:21 p.m.
Remarks: *freshly injection moulded

Niederzissen, 14.09.2015 Signature: *C. J. Keller*

The raw material used in this material complies with the recommendations of the EU-Guideline 2000/53 of the European Parliament dated 18 September 2000 about old vehicles. It is confirmed herewith that the delivery meets the agreements on receipt of order. The CoA shall not relieve the recipient from his legal incoming goods inspection and is not to be construed as guarantee of specific material properties.

AKRO-PLASTIC GmbH
Member of the Feddersen Group

Industriegebiet Brühlthal Ost P.O.B. 67
Im Stiefelfeld 1 56649 Niederzissen
56551 Niederzissen

Phone: +49 2636 9742-0
Fax: +49 2636 9142-31
info@akro-plastic.com


www.akro-plastic.com
Managing Directors:
Dirk Stenbrink, Andreas Stuber
Chairman of the Supervisory Board: URS/VAT-SInr. DE 81117257

Dr. Matthias van Röm
Commercial Register Koblenz
HRB 12227
URS/VAT-SInr. DE 81117257

The growing use of electronics has made our lives easier and richer in many areas. Electronic components are not just used in smartphones and tablets; integrated circuits (IC) are also increasingly found in motor vehicles. In the automotive industry, it has been observed again and again that at increased temperatures, the service life of the elements and components used decreases. An analysis of prematurely failed components shows that corrosion on the contacts of the ICs is a major cause for the failure.

This causes a reaction in which iodine ions and bromine ions enter into a complex interaction with the intermetallic phases. These ions come from the stabilisation packages of the plastic and are specifically guided through the electrical fields to the locations where they can do their destructive work. One of the major tasks for the automotive industry is to ensure that such failures do not occur. AKRO-PLASTIC GmbH have risen to the challenge by developing a new product line of electrochemically neutral polyamide compounds with heat stabilisers and lubricants without halogens or metal soaps. This product line bears the extension "EN", for electrically neutral.

During acceptance testing on the production line, AKRO-PLASTIC state a bromine and iodine content of <1 ppm on all certificates of analysis for the EN product line (Fig. 5). We therefore provide what is likely the highest resolution analytics in day-to-day standard applications. Standard elemental analysis methods are typically only capable of identifying ranges of >10 ppm. This method is used in-house on our own production line.

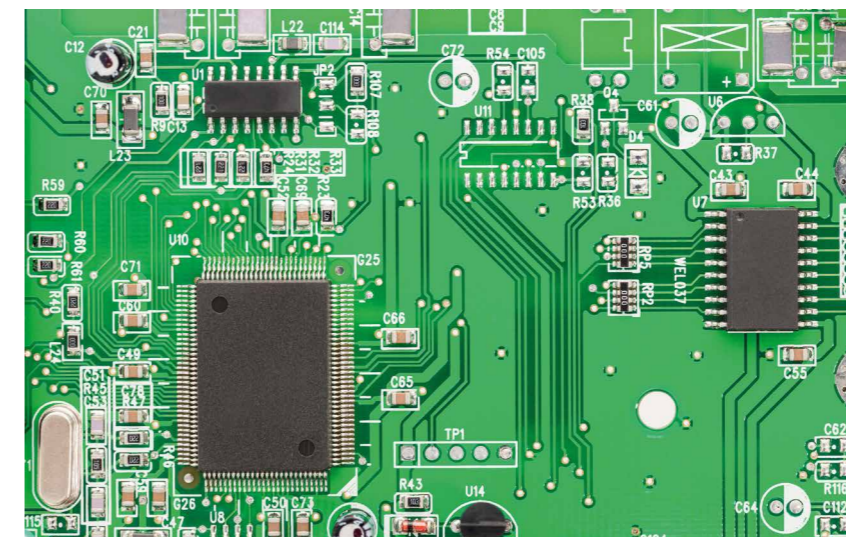


Application circuit board

Processing/Applications

AKROMID® A, B and C can be processed on commercially available injection moulding machines with

standard screws according to the recommendations of the machine manufacturer. Please refer to the

tables below for our recommended machine, mould and dryer settings (see sketch):

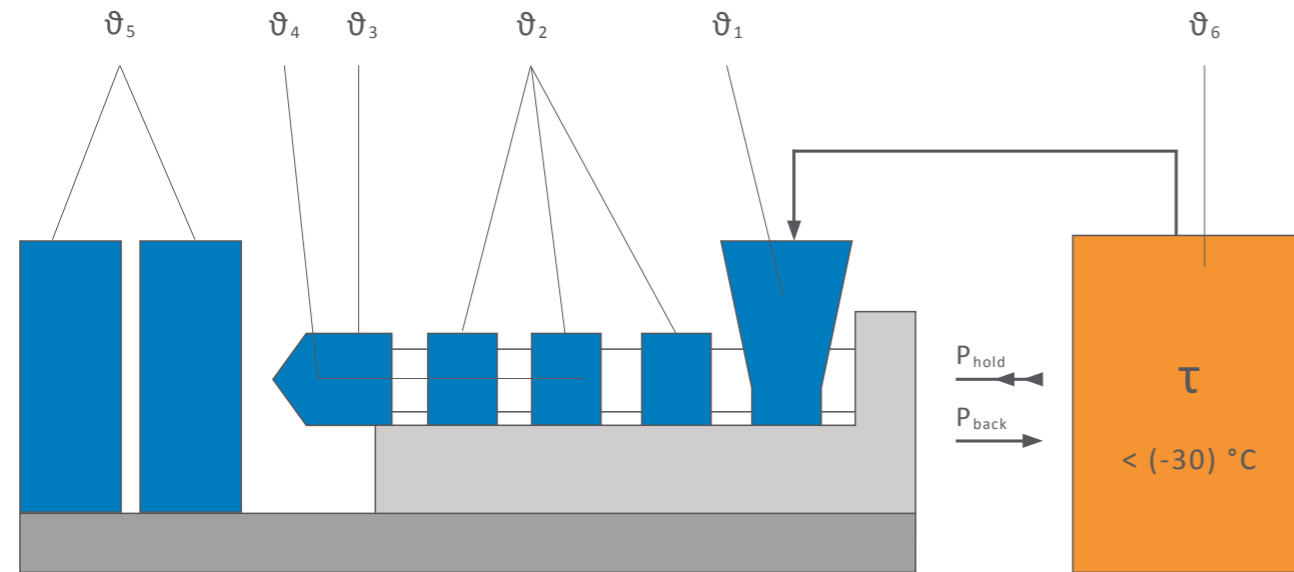


| | | AKROMID® A | AKROMID® B | AKROMID® C |
|-------------------------|-------------------|---------------|---------------|---------------|
| Flange | θ_1 | 60 – 80 °C | 60 – 80 °C | 60 – 80 °C |
| Sector 1 – sector 4 | θ_2 | 260 – 310 °C | 220 – 300 °C | 260 – 300 °C |
| Nozzle | θ_3 | 270 – 310 °C | 230 – 300 °C | 260 – 300 °C |
| Melt temperature | θ_4 | 280 – 310 °C | 240 – 300 °C | 270 – 300 °C |
| Mould temperature | θ_5 | 80 – 100 °C | 80 – 100 °C | 80 – 100 °C |
| Drying | θ_6 | 0 – 4 h | 0 – 4 h | 0 – 4 h |
| Holding pressure, spec. | P_{hold} | 300 – 800 bar | 300 – 800 bar | 300 – 800 bar |
| Back pressure, spec. | P_{back} | 50 – 150 bar | 50 – 150 bar | 50 – 150 bar |


The specified values are for reference values. For increasing filling contents the higher values should be used. For drying, we recommend using only dry air or a vacuum dryer. Processing moisture levels between 0.02 and 0.1 % are recommended. For AKROMID® delivered in bags, no predrying is required when properly stored. It is recommended to use opened bags completely. Material processed from silo or boxes requires a minimum drying time of 4 h.

Disclaimer: All specifications and information given in this brochure are based on our current knowledge and experience. A legally binding promise of certain characteristics or suitability for a concrete individual case cannot be derived from this information. The information supplied here is not intended to release processors and users from the responsibility of carrying out their own tests and inspections in each concrete individual case. AKRO®, AKROMID®, AKROLEN®, AKROLOY®, AKROTEK® and ICX® are registered trademarks of the Feddersen Group.


Flow length AKROMID® A

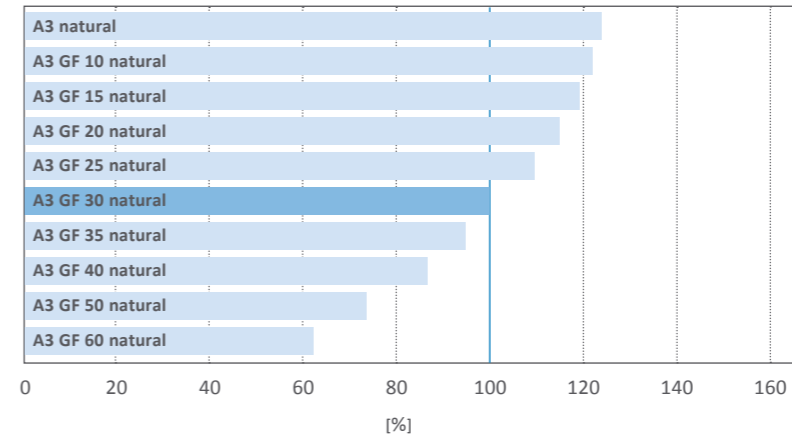

Flow length AKROMID® B

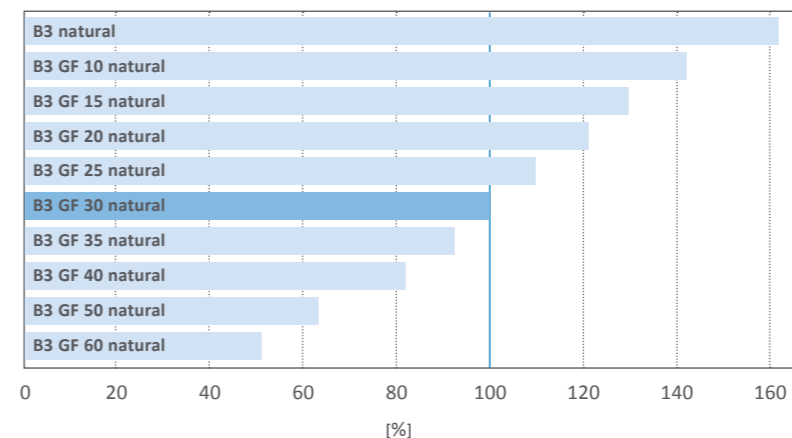


Comparison of AKROMID® C GF flow length

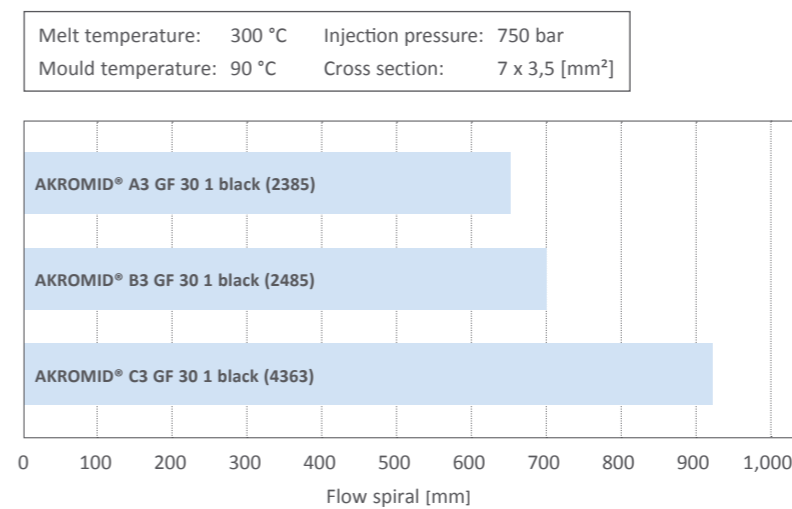

Taking account of the processing conditions listed here, AKROMID® A, B and C can be used to make a number of sophisticated engineering parts, depending on the achievable flow paths. Here are a few examples which show that different industries are already successfully using this material in their innovative products.

Due to their excellent surface quality, AKROMID® B compounds (PA 6) are choice materials in the sports and leisure sector. Since the temperature level for many automotive applications (shift gates, for instance) requires materials with a higher heat distortion temperature, PA 6.6-based AKROMID® A compounds have become well-established here, unless lower loads allow the use of other AKROMID® compounds.

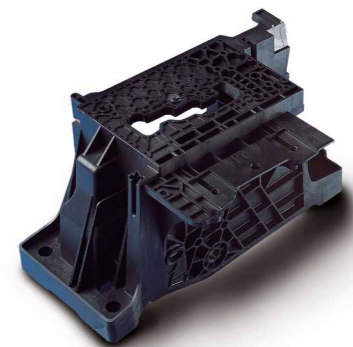

Gear shift gate made from AKROMID® A3 GF 30 1 black (2385)*

* Thermal aging stabilisation 1 (long term stability up to 130 °C)
Thermal aging stabilisation 5 (long term stability up to 150 °C), subdued colors only



Lambda sensor holder made from AKROMID® B3 GF 30 1 black (2485)

Applications

In order to expand the range of possible applications with AKROMID® A, B and C to include specific production methods, materials have been developed which are specifically suited to fluid injection technology (FIT). This technology is used to manufacture components with relatively thick walls as well as components with hollow spaces. The fluid used can be either gas (GIT) or water (WIT). Materials designated as "WIT" are used when special attention is required for the formation of particularly high-quality surface finishes in the interior.

Thus components which are used in the engine cooling circuit of a number of different motor vehicles are made of our AKROMID® A3 GM 20/10 4 WIT black (4529). The advantages of this material lie in the extremely easy processability of our AKROMID®, which was optimised specifically for the water-injection process. The material is used in both the reverse-pressure mass process and the overflow cavity process.

The most important step, irrespective of the selected method, remains the use of an appropriate design of the component and, of course, the material. We are happy to assist you in choosing a process and material suitable for your application. Because one thing is certain when dealing with custom processes: the process complexity increases. Our materials are produced within such narrow production tolerances that our AKROMID® WIT and GIT blends guarantee a stable process. But it isn't just the reproducibility which exceeds that of most of our competitors; so too does our process window. A sophisticated polymer technology enables us to lower the recrystallisation point of the GIT and WIT blends without negatively impacting the crystallinity. In the DSC curve shown here, the AKROMID® GIT variant demonstrates a nearly 15 K lower recrystallisation temperature with the same recrystallisation enthalpy (see Fig. 1).


The result of this modification is useful not only for gas-injection applications but also for standard injection-moulding applications. The illustrated component section shows the high surface quality which can be achieved with AKROMID® A3 GF 15 1 GIT black (4620).



Valve seat with AKROMID® A3 GF 15 1 GIT modification

DSC – comparison of AKROMID® STD / GIT


(Fig. 1)

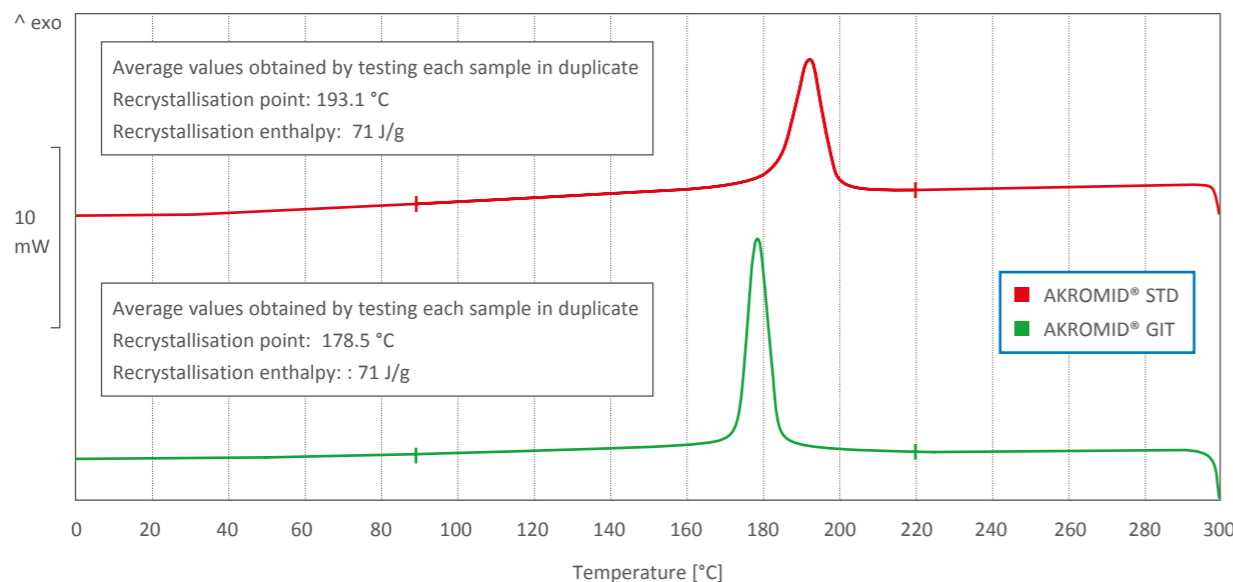

Drying


Drying as a function of material moisture

(Fig. 7)

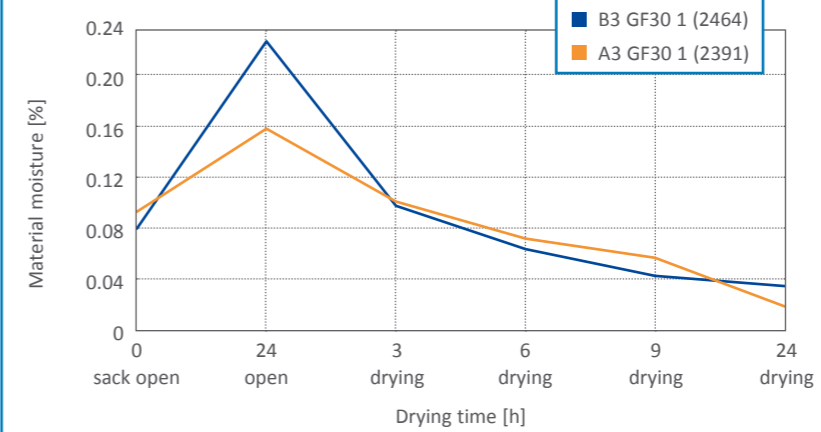


Drying as a function of flow spiral

(Fig. 8)

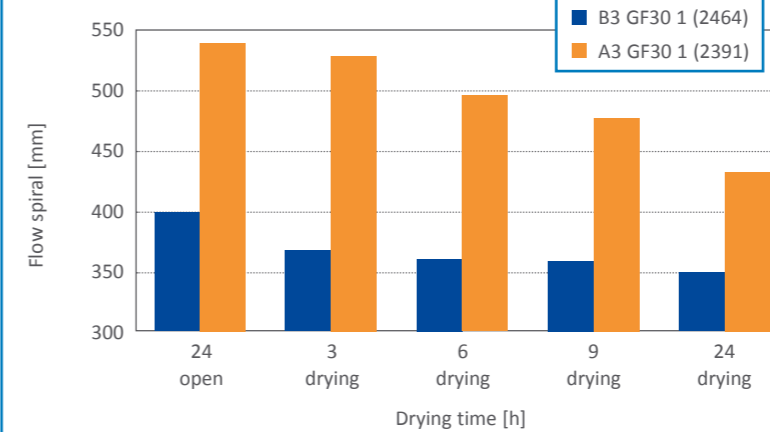

Example of undesirable surface markings

(Fig. 9)

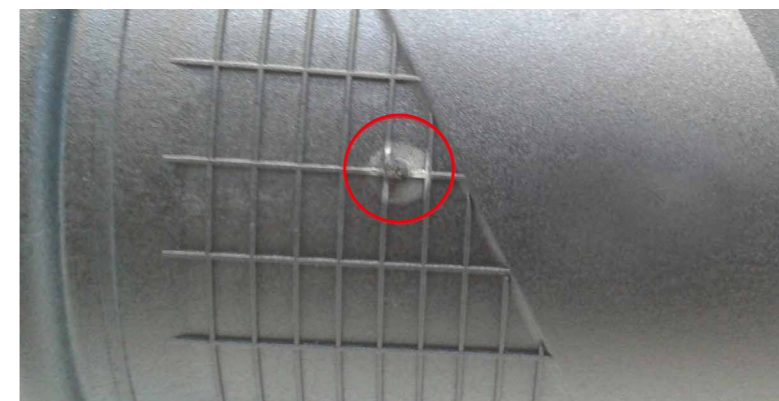

Most plastic pellets, and polyamide 6 and 6.6 in particular, absorb moisture from the air during storage. An excessive moisture content in the plastic pellet can lead to problems during injection moulding. Visible streaks or bubbles can appear on the component surface, for example. As a further secondary effect, due to the presence of water, insufficiently dried pellets can break down hydrolytically during the plastification process.

One might therefore conclude that long drying times are favourable in every instance for the processing of polyamides. Yet this is not the case. During injection moulding, component defects can be caused not only by too much moisture; too little moisture in the pellet can also result in undesirable side effects. Thus for optimal processing, polyamides require a residual moisture content of at least 0.02 %, and up to 0.1 %, for example; quite often, however, the pellet is overly dried, resulting in decreased flowability of the melt (see Fig. 7). Problems with the filler performance are a possible consequence. Moreover, undesirable surface markings can also occur (see Fig. 9).

Drying of AKROMID® pellets made of foil-laminated PE sacks is not necessary, provided the pellet is removed from an undamaged container. It must be ensured that the container has reached ambient temperature prior to opening in order to prevent the formation of condensate. Dried pellets should be processed as quickly as possible and whilst still hot. If the containers are open, the required drying time can increase significantly due to moisture absorbed from the air.

Trouble shooting

For effective trouble shooting it is desirable to be able to clearly attribute a defect to a certain symptom.

We have listed the most frequent cases alphabetically in the table below. Corrective actions are divided

into the areas of processing and mould/finished part and listed in order of probability.

| Symptom | Description | Process and processing optimisation | Mould and part optimisation |
|--|--|--|---|
| Flaking, scaling, lamination, delamination | Surface layers can be pulled off due to delamination | Check material for contamination, reduce or graduate injection speed, increase back pressure, increase mould and melt temperature | Smooth gate transitions with radius |
| Weld line | Line marks formed by the meeting of melting fronts | Increase mould and melt temperature, increase back and holding pressure, increase injection speed | Check mould ventilation, move gate, increase surface roughness |
| Diesel effect | Discoloration (burning) at the point of fill | Decrease injection speed and pressure, gradually towards the point of fill reduce or avoid screw retraction entirely | Check mould venting and, if required, increase |
| Sink marks | Surface recesses on the reverse side of ribs, domes or changes of wall thickness | If applicable, increase metering stroke, increase holding pressure and time, optimise injection speed | Enlarge or move gate, improve mould temperature control, optimise wall thickness or rib ratio, shorten flow paths |
| Color streaks (with use of masterbatch) | Locally limited color changes on the surface | Local surface color variations, increase back pressure and screw speed, change pigment size, if necessary use polymer specific masterbatch | Change gate size, use shear/mixing charge |
| Moisture streaks | Silvery streaks in the direction of flow | Dry material sufficiently, increase mould temperature, degas through the cylinder (vented) | |

| Symptom | Description | Process and processing optimisation | Mould and part optimisation |
|--------------------|---|---|--|
| Jetting | Meandering surface pattern due to lack of wall adhesion of melt | Reduce injection speed in first stage significantly, increase mould temperature, decrease melting temperature | Change location or geometry of gate, inject against rebounding surface |
| Glass fibre streak | Rough surface, glass fibres visible on the surface, greying | Increase holding pressure and time, increase injection speed, increase mould and melt temperature, increase back pressure and screw speed | |
| Flash | Over-injection at the parting line and valves, inserts and ejectors | Increase mould clamping force, reduce dwell pressure and time, stage injection speed | Improve rigidity of mould, check for wear |
| Air streaks | Silvery streaks at ribs, domes and wall thickness changes | Reduce injection speed, increase back pressure and screw speed, reduce or avoid screw retraction entirely | Round off sharp edges, change location of gate, check contact of nozzle with mould and contact surface of nozzle in cylinder |
| Voids | Vacuum inclusions inside the part | Increase back pressure, increase holding pressure and time, reduce injection speed, increase metering distance and melt cushion | Enlarge gate, move closer to mass accumulation, reduce material accumulation |
| Matt areas | Dull surface in the gate area | Reduce injection speed, graduate quicker towards end of filling | Enlarge gate, round off sharp edges at gate |
| Burn streaks | Dark streaks due to thermally damaged material | Reduce injection speed, reduce back pressure and screw speed, reduce melt temperature (hot runner temperature) | Enlarge flow cross-section, optimise gates |

Resistance to media

The information regarding chemical resistance are subjective ratings based on resistance experiments

according to standards DIN EN ISO 175, DIN EN ISO 11403-3, DIN EN ISO 22088.

The information is intended for an initial assessment only.

| Medium | Temp. (°C) | Conc. (%) | pass | fail |
|---------------------------------|------------|-----------|------|------|
| Acetaldehyde | 23 | 40 | | • |
| Acetone | 23 | 100 | • | |
| Acetonitrile | 23 | 100 | • | |
| Acrylonitrile | 23 | 100 | • | |
| Allyl alcohol | 23 | 96 | | • |
| Formic acid | 23 | 2 | | • |
| Ammonia, aqueous | 23 | 10 | • | |
| Amyl alcohol | 23 | 100 | • | |
| Benzine | 23 | 100 | • | |
| Benzine | 40 | 100 | | • |
| Benzene | 23 | 100 | • | |
| Boric acid | 23 | 10 | • | |
| Boric acid | 23 | 100 | | • |
| Brake fluid (DOT 4) | 130 | 100 | | • |
| Brake fluid (DOT 4) | 23 | 100 | • | |
| Biodiesel | 23 | 100 | • | |
| Calcium chloride, aqueous | 23 | 10 | • | |
| Calcium chloride, alcoholic | 23 | 10 | | • |
| Chlorine | 23 | 100 | | • |
| Chloroacetic acid | 23 | 50 | | • |
| Hydrogen chloride, gas | 23 | 100 | | • |
| Chlorine water | 23 | 100 | | • |
| Chromic acid | 23 | 10 | | • |
| Cyclohexane | 23 | 100 | • | |
| Cyclohexanol | 23 | 100 | • | |
| Dichloro-Acetic acid | 23 | 50 | | • |
| Diesel fuel (DIN EN 590) | 23 | 100 | • | |
| Natural gas | 23 | 100 | • | |
| Acetic Acid | 23 | 20 | • | |
| Ethanol | 23 | 96 | • | |
| Ethyl acetate | 23 | 100 | • | |
| Ethylene glycol/water | 120 | 50 | | • |
| Formaldehyde, aqueous | 23 | 10 | • | |
| Transmission oil (ATF m 1375.4) | 150 | 100 | • | |
| Glycerin | 23 | 100 | • | |
| Urea, aqueous | 23 | 20 | • | |

| Medium | Temp. (°C) | Conc. (%) | pass | fail |
|------------------------------------|------------|-----------|------|------|
| Hydraulic oil H and HL (DIN 51524) | 100 | 100 | • | |
| Iso-octanol | 23 | 100 | • | |
| Isopropanol | 23 | 100 | • | |
| Caustic potash solution, aqueous | 23 | 50 | • | |
| Potassium chloride, aqueous | 23 | 10 | • | |
| Potassium permanganate, aqueous | 23 | 10 | | • |
| Carbonic acid | 60 | 100 | • | |
| Methanol | 23 | 100 | • | |
| Methylene chloride | 23 | 100 | | • |
| Motor oil (SAE 10W-40) | 130 | 100 | • | |
| Motor oil (SAE 10W-40) | 23 | 100 | • | |
| Sodium chloride, aqueous | 23 | 10 | • | |
| Sodium hydroxide solution, aqueous | 23 | 1 | • | |
| Sodium hypochlorite, aqueous | 23 | 10 | | • |
| Oleic acid | 23 | 100 | • | |
| Ozone | 23 | 100 | | • |
| Phenol | 23 | 100 | | • |
| Phosphoric acid | 23 | 30 | | • |
| Nitric acid | 23 | 40 | | • |
| Hydrochloric acid | 23 | 36 | | • |
| Carbon disulphide | 23 | 100 | • | |
| Sulphuric acid | 23 | 96 | | • |
| Sulphuric acid | 23 | 5 | | • |
| Seawater | 23 | 100 | • | |
| Silicone fluid | 23 | | • | |
| Super-grade petrol (DIN 51600) | 23 | 100 | • | |
| Carbon tetrachloride | 23 | 100 | • | |
| Toluol | 23 | 100 | • | |
| Water | up to 50 | 100 | • | |
| Hydrogen peroxide | 23 | | | • |
| Xylol | 23 | 100 | • | |
| Zinc chloride, aqueous | 23 | 50 | | • |
| Citric acid | 23 | 10 | • | |

Resistant means:


Unrestricted resistance under the specified conditions.

Not resistant means:

In spite of short-term resistance the material may be damaged, in case of prolonged contact there will be quickly visible chemical degradation. In any case, AKROMID® intended

for use with one of the listed media may only be used after practical testing.

We will be pleased to meet you!

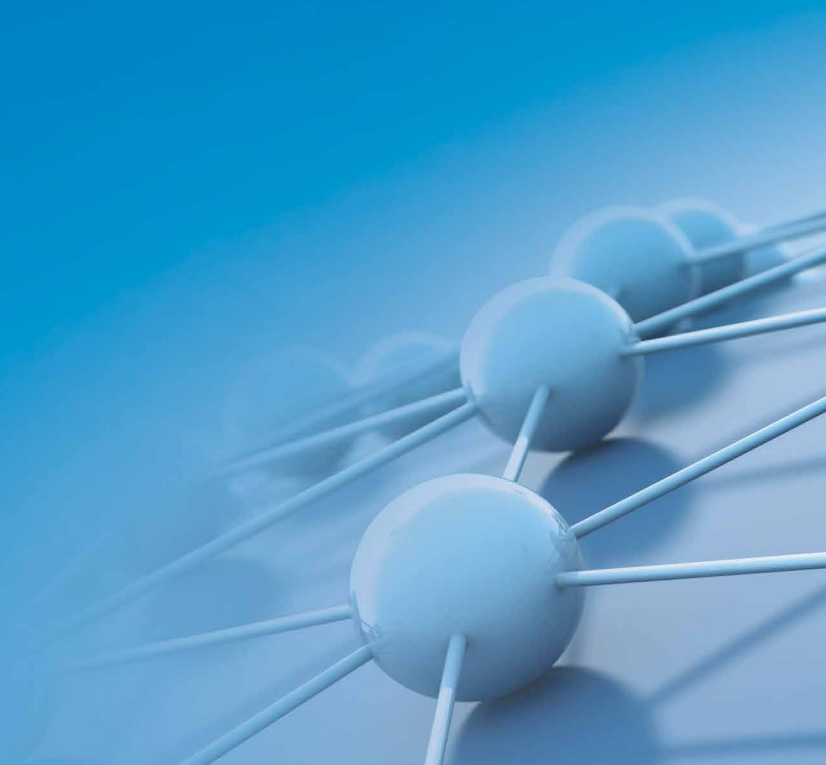

AKRO-PLASTIC GmbH

Member of the Feddersen Group

Industriegebiet Brohltal Ost

Im Stiefelfeld 1

56651 Niedertzissen

Germany

Phone: +49(0)2636-9742-0

Fax: +49(0)2636-9742-31

info@akro-plastic.com

www.akro-plastic.com

Here you can find
the latest version
of our brochure:



For more locations, visit www.akro-plastic.com